



НҮҮРСНИЙ ОВООЛГЫН ҮЗҮҮЛЭЛТ

№ ETT_SP_20006



ISO 45001:2018



ISO 9001:2015



ISO 14001:2015



НҮҮРСНИЙ ОВООЛГЫН ЧАНАРЫН ДУНДАЖ ҮЗҮҮЛЭЛТ

<p>НИЙТ ЧИЙГ (ar)</p> <p>3.52%</p> <p>(-0.8; +0.8)</p>	<p>ҮНСЛЭГ (db)</p> <p>18.91%</p> <p>(-3.1; +4.3)</p>	<p>ДЭГДЭМХИЙ (daf)</p> <p>33.09%</p> <p>(-1.0; +1.4)</p>
<p>НИЙТ ХҮХЭР (db)</p> <p>1.17%</p> <p>(-0.4; +0.5)</p>	<p>БАРЬЦАЛДАХ ЧАНАР</p> <p>68.0</p> <p>(-14; +15)</p>	<p>НҮҮРСНИЙ ХЭМЖЭЭ</p> <p>88.6</p> <p>МЯН.ТН</p>

Овоолгын насжилт 696 хоног
 НҮҮРСНИЙ ОВООЛГЫН ШИНЖИЛГЭЭНИЙ ҮР ДҮН

ALS GROUP LLC
 Mongol National Building, 2nd khoroо
 Chinggis Avenue, Khan Uul District
 Ulaanbaatar, Mongolia
 Tel: +976 70 007667



CERTIFICATE OF ANALYSIS
 23J06-TT

CLIENT: Erdenes Tavan Tolgoi JSC
 ADDRESS: Finance Center, Jigjidjav-8
 1st khoroо, Chingelbal District
 Ulaanbaatar, Mongolia
 ATTN: Bilguunmantul
 PROJECT NO.: xxx
 LAB. JOB NO.: 23J06-TT
 NO. SAMPLES: 8
 Notes/Comments: xxx

SAMPLES RECEIVED: 01/Oct/23
 INSTRUCTIONS RECEIVED: 01/Oct/23
 DATE OF REPORT: 03/Oct/23
 STATUS OF REPORT: FINAL
 ANALYSIS COMPLETE: 03/Oct/23
 PREPARATION CODE: CRUSH-01, 02; MILL-01
 ANALYSIS CODE: 1_COOKING COAL
 TM, ASH, MOIS, VOL,
 TSUL, CKIN

APPROVED BY: Laboratory Manager


Checked by: Chief Chemist

These test results are representative only of the sample received in the laboratory.

STANDARD METHOD	SAMPLE NO.	AS RECEIVED BASIS												AIR DRIED BASIS						DRY BASIS						DRY, ASH-FREE BASIS				Coal Caking Index (CKIN)	
		GB/T 211	GB/T 212	GB/T 212	GB/T 212	ISO 19579	GB/T 212	GB/T 212	GB/T 212	GB/T 212	ISO 19579	GB/T 212	GB/T 212	GB/T 212	ISO 19579	GB/T 212	GB/T 212	ISO 19579	GB/T 212	GB/T 212	ISO 19579	GB/T 212	GB/T 212	ISO 19579	GB/T 5447	GB/T 5447					
		Total Moisture (TM)	Ash (ASH)	Volatile Matter (VOL)	Fixed Carbon (FC)	Total Sulphur (TSUL)	Moisture (MOIS)	Ash (ASH)	Volatile Matter (VOL)	Fixed Carbon (FC)	Total Sulphur (TSUL)	Ash (ASH)	Volatile Matter (VOL)	Fixed Carbon (FC)	Total Sulphur (TSUL)	Ash (ASH)	Volatile Matter (VOL)	Fixed Carbon (FC)	Total Sulphur (TSUL)	Volatile Matter (VOL)	Fixed Carbon (FC)	Total Sulphur (TSUL)			S1	S3					
		%																													
1	ETT_SP_20006-RS-1-1	3.81	15.19	27.91	53.09	0.93	0.93	15.45	28.74	54.68	0.96	15.79	29.01	55.19	0.97	34.46	65.54	1.15	75												
2	ETT_SP_20006-RS-1-2	3.28	15.60	26.48	54.64	0.77	0.64	16.00	27.15	56.02	0.79	16.13	27.38	56.49	0.80	32.64	67.36	0.95	83												
3	ETT_SP_20006-RS-1-3	3.72	16.64	26.65	52.99	1.16	0.95	17.12	27.42	54.52	1.19	17.28	27.68	55.04	1.21	33.46	66.54	1.46	74												
4	ETT_SP_20006-RS-1-4	4.33	22.18	25.00	48.48	1.30	1.07	22.94	25.86	50.14	1.34	23.19	26.14	50.68	1.36	34.03	65.97	1.77	57												
5	ETT_SP_20006-RS-2-1	2.75	20.38	24.65	52.23	0.88	0.77	20.79	25.15	53.29	0.90	20.95	25.34	53.71	0.90	32.06	67.94	1.14	71												
6	ETT_SP_20006-RS-2-2	2.74	20.08	25.13	52.05	1.26	0.99	20.44	25.59	52.99	1.28	20.64	25.84	53.52	1.29	32.56	67.44	1.63	59												
7	ETT_SP_20006-RS-2-3	3.53	16.14	25.89	54.44	1.16	1.04	16.56	26.55	55.85	1.19	16.73	26.83	56.44	1.21	32.23	67.77	1.45	68												
8	ETT_SP_20006-RS-2-4	4.28	19.97	25.36	50.39	1.62	1.12	20.63	26.19	52.06	1.68	20.86	26.49	52.65	1.70	33.47	66.53	2.14	54												

QUALITY ASSURANCE/QUALITY CONTROL DATA

STD/LEWS-20/21	ASH	VOL	TSUL
Certified Value	10.70	20.35	0.696
Standard Deviation	0.059	0.204	0.0136
Unit	%	%	%
Analyzed value	10.68	20.34	0.696

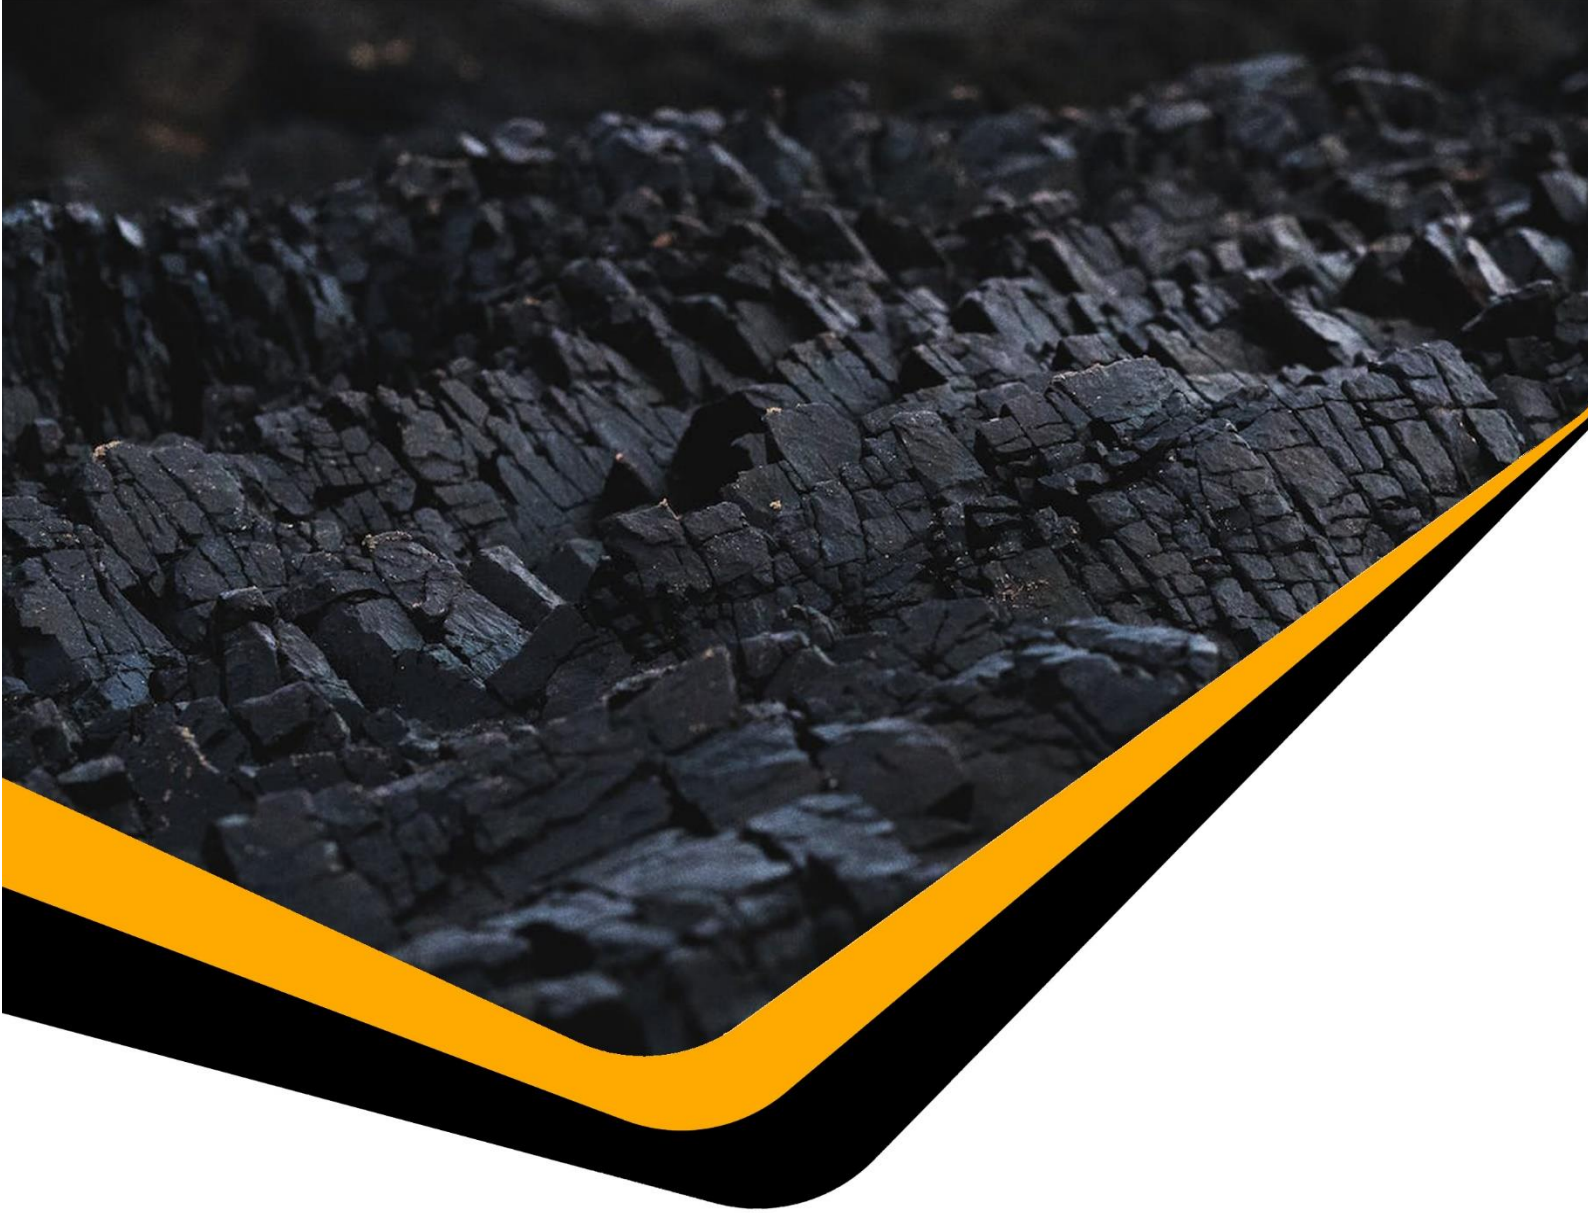

ISO 45001:2018



ISO 9001:2015



ISO 14001:2015



www.ett.mn



75055555
1800-1072



Финанс төв, 1-р хороо,
Чингэлтэй дүүрэг,
Улаанбаатар хот

